

Liquid-crystalline methanofullerodendrimers which display columnar mesomorphism

Natacha Maringa,^a Julie Lenoble,^a Bertrand Donnio,^b Daniel Guillon^{*b} and Robert Deschenaux^{*a}

Liquid-crystalline methanofullerodendrimers were synthesized *via* the Bingel addition reaction of mesomorphic malonate derivatives and C₆₀. Second- and third-generation poly(benzyl ether) dendrons were selected as liquid-crystalline promoters to induce columnar mesomorphism. Based on a convergent and modular synthetic methodology, symmetrical (two identical dendrons) and non-symmetrical (two different dendrons) dendrimers were prepared, as well as hemidendrimers (only one dendron). The liquid-crystalline properties of the malonates and fullerodendrimers were investigated by polarized optical microscopy, differential scanning calorimetry, and X-ray diffraction. All the malonates give rise to hexagonal columnar phases of *p6mm* symmetry. As for the fullerodendrimers, the second-generation hemidendrimer shows a rectangular columnar phase of *c2mm* symmetry, while the other materials give rise to hexagonal columnar phases of *p6mm* symmetry.

Introduction

[60]Fullerene-containing liquid crystals¹ displaying columnar phases are of interest for electronic and optoelectronic applications (*e.g.*, one-dimensional electron transportation). So far, only a few examples have been reported in the literature: columnar phases were obtained by (1) attaching five aromatic groups around one pentagon of [60]fullerene (C₆₀),² (2) complexing C₆₀ with liquid-crystalline dendritic porphyrins,³ (3) mixing two non-mesomorphic compounds, one of which is a C₆₀-triphenylene derivative,⁴ and (4) functionalizing C₆₀ with mesomorphic dendrimers.⁵

The use of liquid-crystalline dendrimers as mesomorphic promoters to functionalize C₆₀ has two advantages: firstly, the fullerene cores are isolated from each other, and thus, C₆₀-C₆₀ interactions (responsible for the formation of aggregates), which may be detrimental to the formation of mesophases, are reduced or even suppressed,⁶ and secondly, the supramolecular organization within the liquid crystal state can be controlled owing to the numerous possibilities which can be used to modify the structure of the dendrimers (generation, polarity and stiffness of the core, number of branching units, nature of the end-groups).⁷

With a view to designing liquid-crystalline fullerenes which display columnar phases, we selected poly(benzyl ether) dendrons⁸ as a source of mesomorphism. In a first study,^{5a} C₆₀

was functionalized with second-generation poly(benzyl ether) dendrons; rectangular columnar phases (*c2mm* symmetry) were obtained. Within the rectangular columnar phases, the columns were formed by a hexagonal close compact packing of C₆₀, surrounded by the dendrons, the alkyl chains forming the outer layer of the columns. In a second study,^{5b} Janus-type fulleropyrrolidines bearing a poly(benzyl ether) dendron functionalized with alkyl chains and a poly(aryl ester) dendron functionalized with cyanobiphenyl units were synthesized. The generation of each dendron was varied, and, depending on the generation, smectic (C and/or A) or rectangular columnar (*c2mm* symmetry or *p2gg* symmetry) phases were obtained. We have demonstrated that the supramolecular organization of the liquid-crystalline fullerodendrimers within the mesophases is governed by (1) the “aliphatic terminal chains/mesogenic groups” ratio, (2) effective lateral interactions between the cyanobiphenyl mesogenic groups, (3) microsegregation of the dendrons, and (4) deformation of the dendritic core. In a third study,⁹ addition of two poly(benzyl ether) dendrons onto C₆₀ led to fulleropyrrolidines which were found to be non-mesomorphic. The absence of liquid-crystalline properties for those materials is the consequence of the formation of materials which lack shape specificity due to conformations induced by C₆₀.

Obviously, the formation of columnar phases for fullerene-containing liquid crystals is not yet fully understood. An important step to better our understanding of the “*structure-supramolecular organization*” relationship for liquid-crystalline fullerodendrimers could be achieved by investigating the properties of methanofullerenes and of their corresponding malonates. Such a study would emphasize the role played by C₆₀ in the formation, structure, and stability of the columnar phases.

We report, herein, the synthesis, characterization, mesomorphic properties, and supramolecular organization of methanofullerodendrimers **1–5** (Charts 1 and 2) and compare their properties with those of the corresponding malonates.

^aInstitut de Chimie, Université de Neuchâtel, Avenue de Bellevaux 51, Case Postale 158, 2009 Neuchâtel, Switzerland. E-mail: robert.deschenaux@unine.ch

^bInstitut de Physique et Chimie des Matériaux de Strasbourg, Groupe des Matériaux Organiques, 23 Rue du Loess, BP 43, 67034 Strasbourg Cédex 2, France. E-mail: daniel.guillon@ipcms.u-strasbg.fr

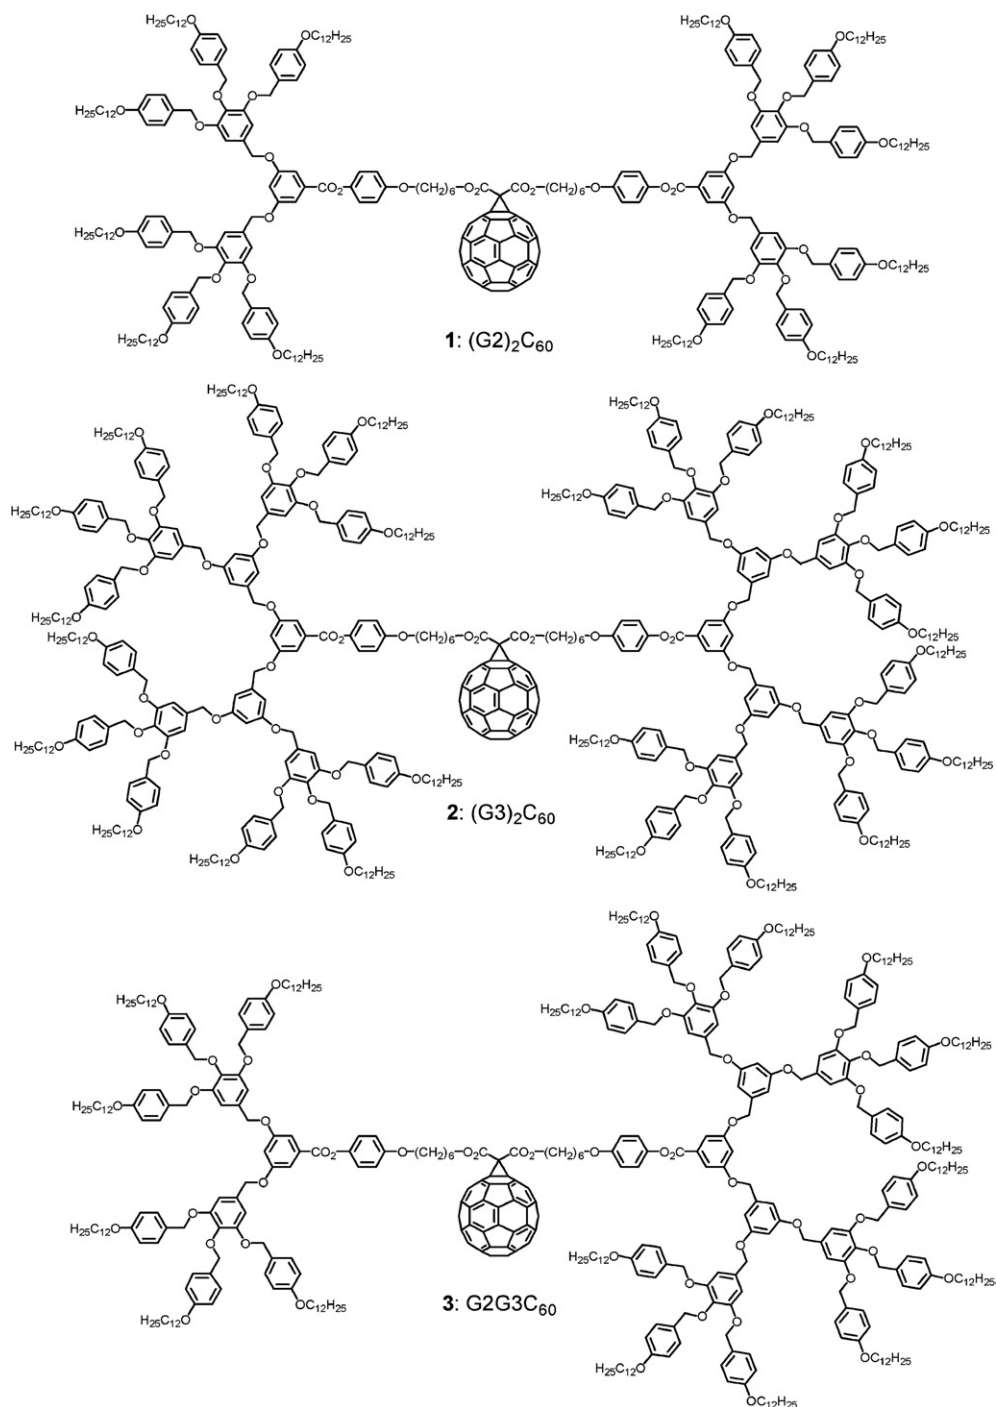


Chart 1

Results and discussion

Design

This study is based on symmetrical [$(G_2)_2C_{60}$ (**1**): two second-generation poly(benzyl ether) dendrons; $(G_3)_2C_{60}$ (**2**): two third-generation poly(benzyl ether) dendrons] and non-symmetrical [$G_2G_3C_{60}$ (**3**): mixed second- and third-generation poly(benzyl ether) dendrons] fullerodendrimers (Chart 1) and fullero-

hemidendrimers [G_2C_{60} (**4**): second-generation poly(benzyl ether) dendron; G_3C_{60} (**5**): third-generation poly(benzyl ether) dendron] (Chart 2).

Synthesis

The dendrons were synthesized *via* a convergent approach.¹⁰ The malonates were added onto C_{60} *via* the Bingel reaction.¹¹ The syntheses of **6**,^{5a} **8**,¹² and **9**^{8b} have already been described elsewhere.

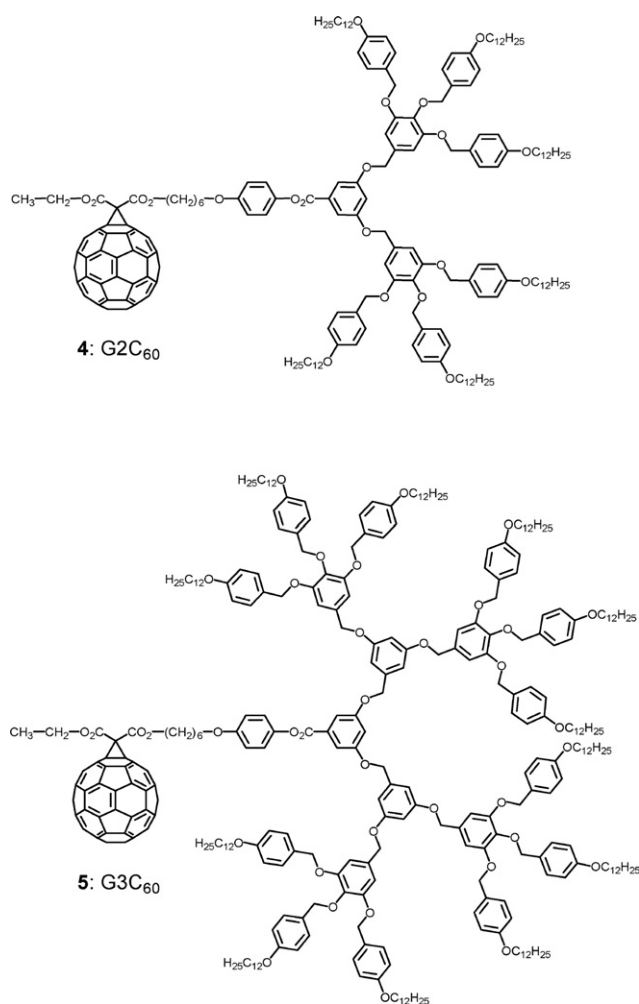


Chart 2

The synthesis of methanofullerene (G2)₂C₆₀ (**1**) is presented in Scheme 1. Condensation of **6** with malonyl chloride gave malonate derivative (G2)₂Mal (**7**), which was added to C₆₀ to give (G2)₂C₆₀ (**1**).

The synthesis of fullerodendrimer (G3)₂C₆₀ (**2**) is illustrated in Scheme 2. Esterification of **8** and **9** in the presence of *N,N'*-dicyclohexylcarbodiimide (DCC), 4-(dimethylamino)pyridinium toluene-*p*-sulfonate (DPTS), and 4-pyrrolidinopyridine (4-Ppy) led to alcohol intermediate **10**, which was reacted with Meldrum acid (2,2-dimethyl-1,3-dioxane-4,6-dione) to furnish carboxylic acid **11**. Esterification of the latter with **10** gave malonate (G3)₂Mal (**12**), which was used in the addition reaction with C₆₀ [\rightarrow (G3)₂C₆₀ (**2**)].

The synthesis of methanofullerene G2G3C₆₀ (**3**) is reported in Scheme 3. Condensation of **6** with Meldrum acid gave **13**, which was esterified with **10** to yield malonate G2G3Mal (**14**). Addition of G2G3Mal (**14**) with C₆₀ furnished G2G3C₆₀ (**3**).

The synthesis of fullerohemidendrimers G2C₆₀ (**4**) (Scheme 4) and G3C₆₀ (**5**) (Scheme 5) required the preparation of G2Mal (**15**) and G3Mal (**16**), respectively, which were obtained by condensation of ethyl malonyl chloride with the appropriate alcohol derivative [**6** \rightarrow G2Mal (**15**), and **10** \rightarrow G3Mal (**16**)]. Addition of G2Mal (**15**) or G3Mal (**16**) to C₆₀ led to G2C₆₀ (**4**) or G3C₆₀ (**5**), respectively.

The structure and purity of all compounds were confirmed by ¹H NMR spectroscopy, GPC (all compounds were found to be monodisperse), UV-vis spectroscopy, and elemental analysis.

Liquid-crystalline properties

The liquid-crystalline and thermal properties of the malonate and fullerene derivatives were investigated by polarized optical microscopy (POM), differential scanning calorimetry (DSC), and X-ray diffraction (XRD). The liquid-crystalline and thermal properties of the intermediates were investigated by POM and DSC. The phase transition temperatures and enthalpies are reported in Table 1. The XRD data are collected in Table 2.


With the exception of (G2)₂C₆₀ (**1**), which is non-mesomorphic, all methanofullerenes display columnar mesomorphism. For (G3)₂C₆₀ (**2**), G2G3C₆₀ (**3**), and G3C₆₀ (**5**), hexagonal columnar phases (*p6mm* symmetry) were obtained, while for G2C₆₀ (**4**) a rectangular columnar phase (*c2mm* symmetry) was detected. A typical texture was observed by POM only for G3C₆₀ (**5**) (Fig. 1). The clearing points indicate that the stability of the mesophase increases with the dendrimer generation [e.g. 68 °C for G2C₆₀ (**4**), 85 °C for G3C₆₀ (**5**)] in agreement with previous results.¹⁴

All the malonates give rise to hexagonal columnar phases (*p6mm* symmetry). Typical textures were observed by POM (Fig. 2 and 3). As expected, the stability of the mesophases increases with the dendrimer generation [clearing points: 88 °C for (G2)₂Mal (**7**), 105 °C for G2G3Mal (**14**), and 109 °C for (G3)₂Mal (**12**); 86 °C for G2Mal (**15**) and 114 °C for G3Mal (**16**)]. As already observed for other compounds,¹⁴ grafting of C₆₀ onto malonates lowered the isotropization temperature, or even suppressed the liquid-crystalline properties [*i.e.* for (G2)₂C₆₀ (**1**)].

X-Ray investigations

Compounds (G2)₂C₆₀ (1**) and (G2)₂Mal (**7**).** Whereas compound (G2)₂C₆₀ (**1**) is not mesomorphic, its malonate precursor (G2)₂Mal (**7**) shows complicated thermal behavior. The sample melts into an amorphous solid, which then crystallizes, and finally melts into the mesophase which was identified as a hexagonal columnar phase. X-Ray diffraction patterns recorded every 5 °C from 40 to 90 °C correspond systematically to a mixture of amorphous, crystalline, columnar and isotropic phases depending upon temperature. This behavior highlights some kinetic and thermodynamic features associated with the phases transformation. This mesophase is thermodynamically unstable.

Compounds (G3)₂C₆₀ (2**) and (G3)₂Mal (**12**).** Above *ca.* 40 °C, both compounds exhibit a hexagonal columnar phase characterized by a series of three sharp and intense diffraction peaks in the small-angle region, in the ratio 1 : $\sqrt{3}$: $\sqrt{4}$. The X-ray diffraction patterns contain also two diffuse signals at *ca.* 8.5 and 4.6 Å, which are attributed to an intracolumnar periodicity along the columnar axis and to the liquid-like arrangement of the terminal aliphatic chains of the dendrons, respectively. The hexagonal cell parameters of both compounds are almost the same, and do not vary significantly as a function of temperature. Therefore, the lateral and stacking arrangements of (G3)₂C₆₀ (**2**) and (G3)₂Mal (**12**) are essentially governed by the dendritic parts.

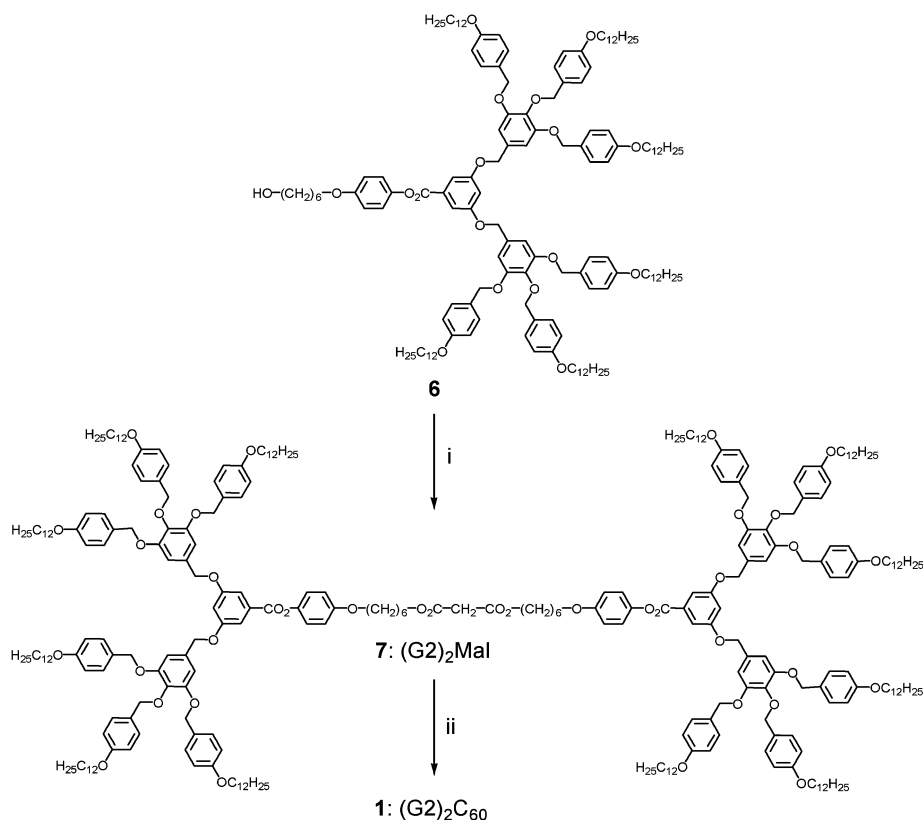

Scheme 1 (i) Malonyl chloride, Et₃N, CH₂Cl₂, r.t., overnight, 27%; (ii) C₆₀, DBU, I₂, toluene, r.t., overnight, 26%. For abbreviations, see ref. 13.

The C₆₀ unit is encapsulated in the dendritic matrix and has no significant influence on the supramolecular organization.

Compounds G2G3C₆₀ (3) and G2G3Mal (14). Both compounds display an amorphous structure at room temperature. A hexagonal columnar phase is obtained above 55 °C. The latter mesophase is characterized by two [for G2G3C₆₀ (3)] or three [for G2G3Mal (14)] sharp diffraction signals in the small-angle region in the ratio 1 : √3 : √4; two diffuse signals at *ca.* 8–8.5 and 4.6 Å are also detected. The hexagonal cell parameters of G2G3C₆₀ (3) and G2G3Mal (14) are similar and do not vary with temperature, confirming that C₆₀ does not influence the molecular organization of the mesophase.


Compounds G2C₆₀ (4) and G2Mal (15). For hemidendrimer G2C₆₀ (4), a rectangular columnar phase forms above 55 °C. A series of nine sharp diffraction signals in the small-angle region has been indexed according to a two-dimensional centered rectangular lattice of *c2mm* symmetry. For precursor G2Mal (15), no clear organization is revealed at room temperature (only diffuse signals are observed). However, above 40 °C, a sharp and intense reflection in the small-angle region is detected, reminiscent of some of the thermal events observed for other compounds described above, and consisting of a crystallization process with slow kinetics, resulting in a mixture of amorphous and crystalline solids. Above 80 °C, the X-ray patterns exhibit three small-angle reflections which can be indexed according to a two-dimensional lattice of a hexagonal columnar phase. The difference of behavior between G2C₆₀ (4) (rectangular columnar

phase) and G2Mal (15) (hexagonal columnar phase) is due to the presence or not of C₆₀, the attachment of which onto the spacer strongly limits the possibility for the dendritic part to self-organize into a hexagonal symmetry.


Compounds G3C₆₀ (5) and G3Mal (16). Hemidendrimer G3C₆₀ (5) exhibits a hexagonal columnar phase above 70 °C deduced from the presence of two sharp reflections in the small-angle region of the X-ray diffraction patterns. These signals can be indexed as the (10) and (11) reflections of a two-dimensional hexagonal lattice. In addition, a diffuse band at 8.5 Å indicates the presence of an average periodicity along the columnar axis. For the corresponding malonate G3Mal (16), the presence of a hexagonal columnar phase from room temperature up to 110 °C is characterized by three reflections indexed as (10), (11) and (20) of a two-dimensional arrangement. The hexagonal cell parameters are similar for both compounds, indicating the primary role of the dendrimer in the supramolecular organization. The C₆₀ unit is effectively encapsulated in G3C₆₀ (5) as it is for (G3)₂C₆₀ (2) and G2G3C₆₀ (3).

Supramolecular organization

Liquid-crystalline malonates. Overall, the self-organization behavior of dendritic (7, 12, 14) and hemidendritic (15, 16) malonates and fullerodendrimers (2–5) within the columnar phases retains the general characteristics of the methyl ester dendrons of second (derived from 6) and third (derived from 9) generation^{8b} used here as building blocks. In particular,

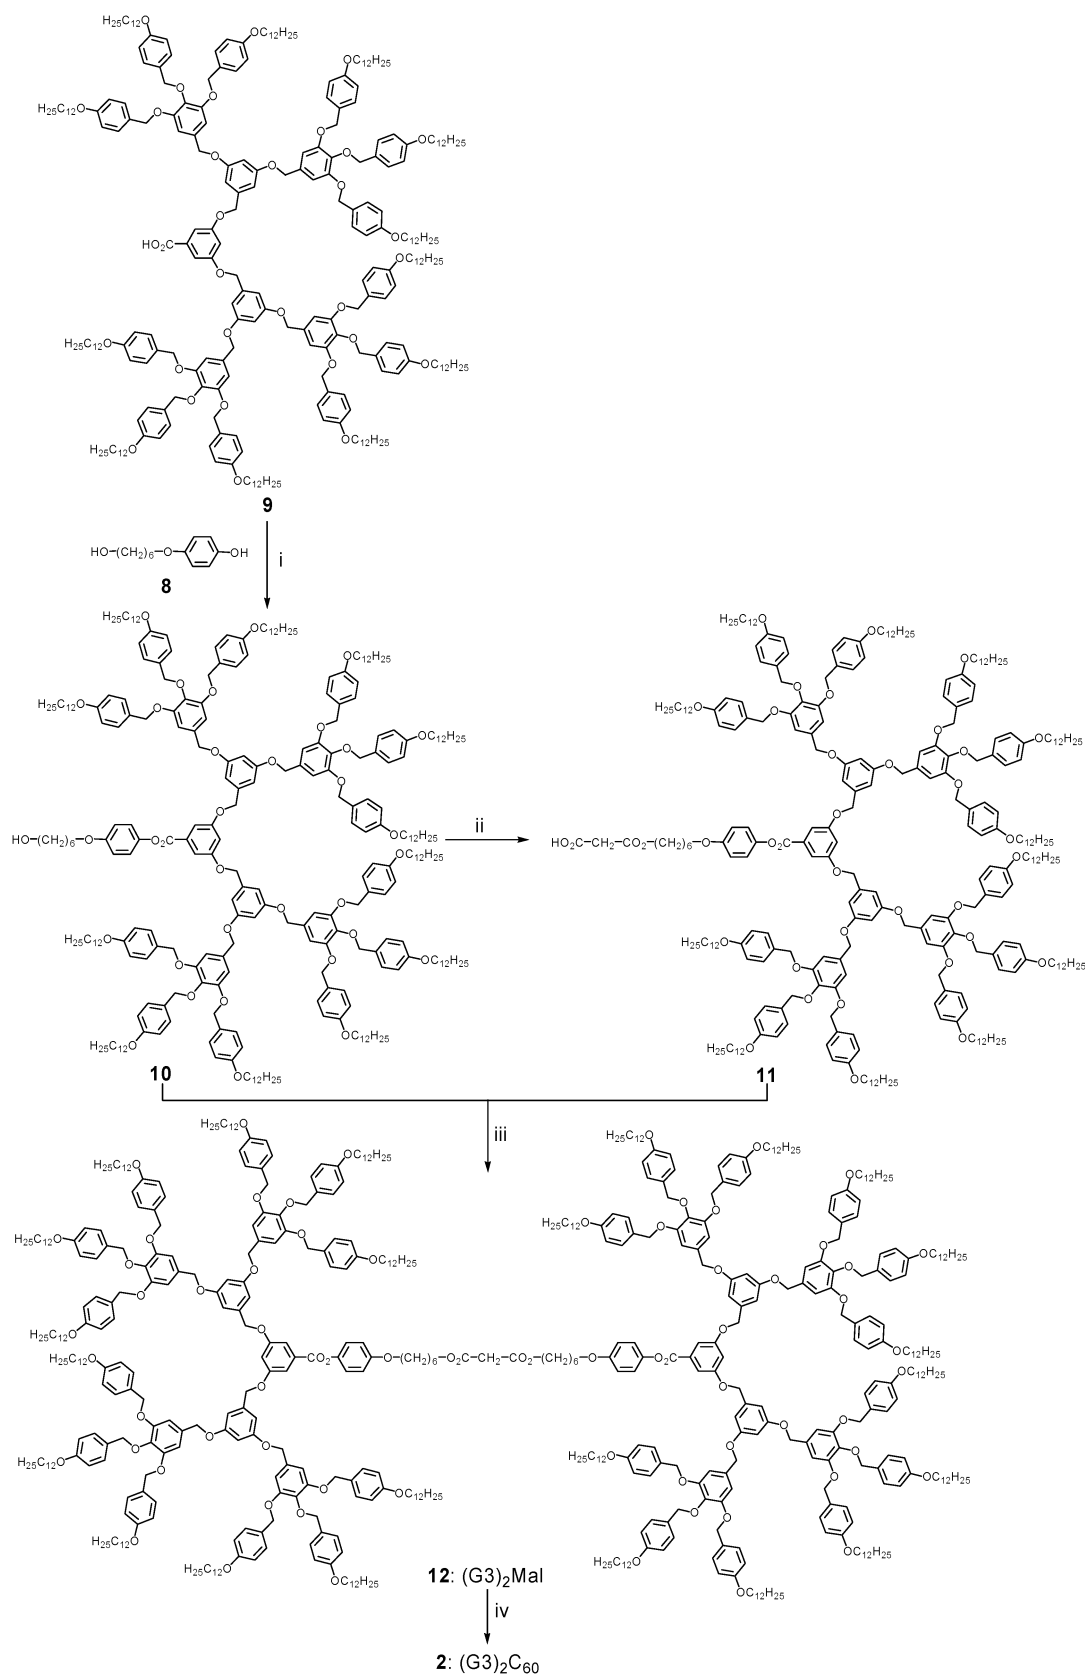

Scheme 2 (i) DCC, DPTS, 4-Ppy, CH₂Cl₂, r.t., overnight, 48%; (ii) Meldrum acid, toluene, 65 °C, 24 h, 89%; (iii) DCC, DPTS, 4-Ppy, CH₂Cl₂, r.t., overnight, 80%; (iv) C₆₀, DBU, I₂, toluene, r.t., overnight, 14%. For abbreviations, see ref. 13.

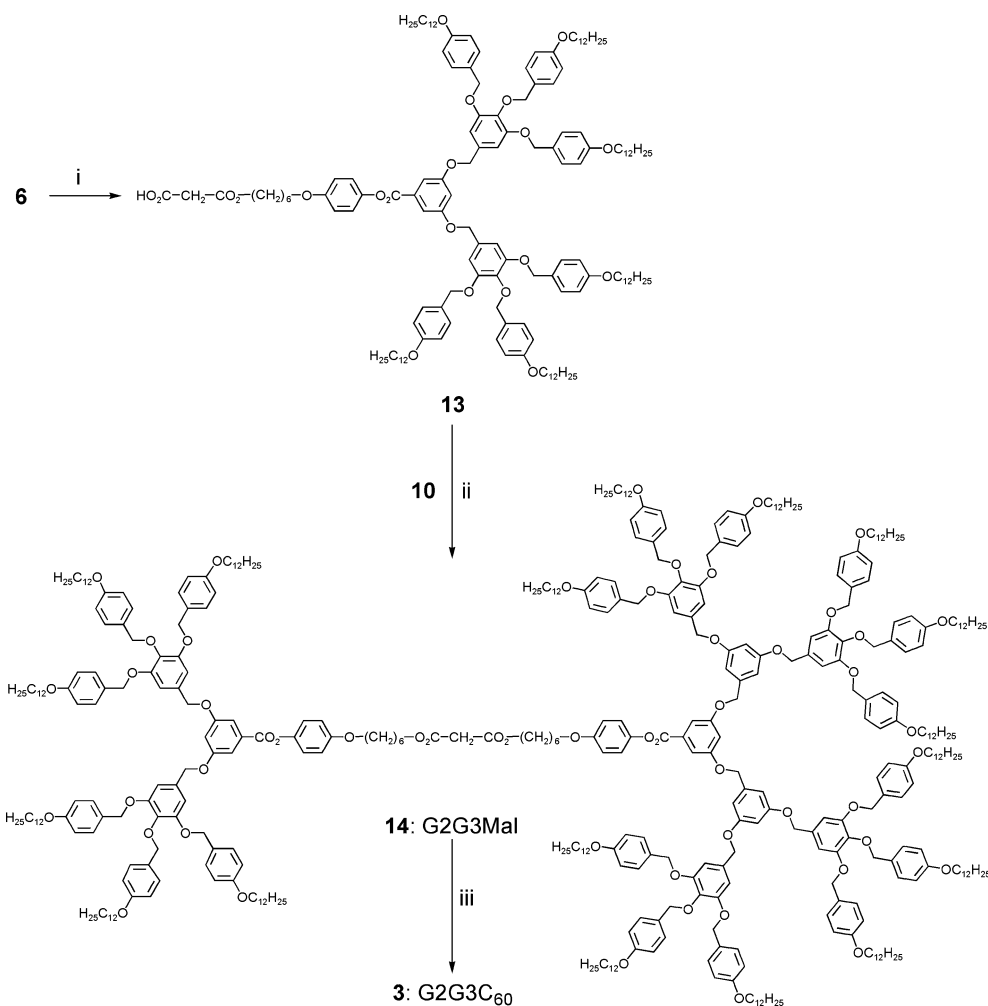


Scheme 3 (i) Meldrum acid, toluene, 65 °C, 24 h, 92%; (ii) DCC, DPTS, 4-Ppy, CH₂Cl₂, r.t., overnight, 76%; (iii) C₆₀, DBU, I₂, toluene, r.t., overnight, 28%. For abbreviations, see ref. 13.


hemidendrimers G2Mal (**15**) and G3Mal (**16**) exhibit comparable mesomorphism (mesophase stability and mesophase parameters) to that of the related esters derived from **6** and **9**, respectively, indicative that a similar packing mode within the hexagonal columnar phases is reproduced. In the flat conformation, G2Mal (**15**) approximates an open fan-shape with a planar angle α at the focal point of *ca.* 120°, whereas G3Mal (**16**) resembles more a semi-disc ($\alpha \sim 180^\circ$), as shown in Scheme 6. Using a straightforward geometrical approach, which takes into account the relationships between the planar angle α , that represents the projection of the tapered dendrons solid angle ω ($\alpha = \omega/2$) and N_D (number of monodendrons or dendritic branches covering the columnar cross-section area, thus per repeat unit) linked through the equation $\alpha = 2\pi/N_D$,^{8b} it was found that 3 molecules of G2Mal (**15**) and 2 molecules of G3Mal (**16**), respectively (here $Z = N_D$), self-associate into an elementary slice of cylindrical column, with calculated thicknesses h'' of 8.6 and 7.9 Å, respectively. The latter values are in good agreement with h' , *i.e.* the average periodicities of the broad halos measured on the diffractograms. In other words, the repeating distance along the columnar axis is defined by the thickness of the disc formed by the dendritic branches. The hard part of the column is filled with the poly(benzyl ether) dendron, and the inner part

accommodates the aliphatic malonate moiety; the columns are surrounded by the molten aliphatic chains.

The connection of two dendrons by a long spacer (leading to dendritic dimers) does not modify the nature of the mesophase, and hexagonal columnar phases are observed for (G2)₂Mal (**7**), (G3)₂Mal (**12**) and G2G3Mal (**14**). However, the mesophase stability, and to some extent the thermal behavior, can be affected upon dimerization as shown by (G2)₂Mal (**7**), for which an unstable thermal phase sequence is observed. In contrast, the behavior of (G3)₂Mal (**12**) is comparable to that of the third-generation methyl ester precursor.^{8b} The mixed derivative G2G3Mal (**14**) also behaves like (G3)₂Mal (**12**) suggesting that the self-organization properties of G2G3Mal (**14**) are dominated by its large side. In both cases, intercolumnar distances are close to each other and to that of G3Mal (**16**) (and also to the monomeric methyl ester precursor^{8b}); similarly, the dimensions of the hexagonal cell of (G2)₂Mal (**7**) and G2Mal (**15**) are identical. As a consequence, the same type of aggregation found for G2Mal (**15**) and G3Mal (**16**) can be deduced for their symmetrical and mixed dimeric structures. Applying the retrostructural analysis⁸ used above, although with $N_D = 2 \times Z$, 1.5 molecular equivalents of (G2)₂Mal (**7**) [equivalent to three (N_D) dendritic parts as in G2Mal (**15**), $\alpha = 120^\circ$ for each dendritic branch],

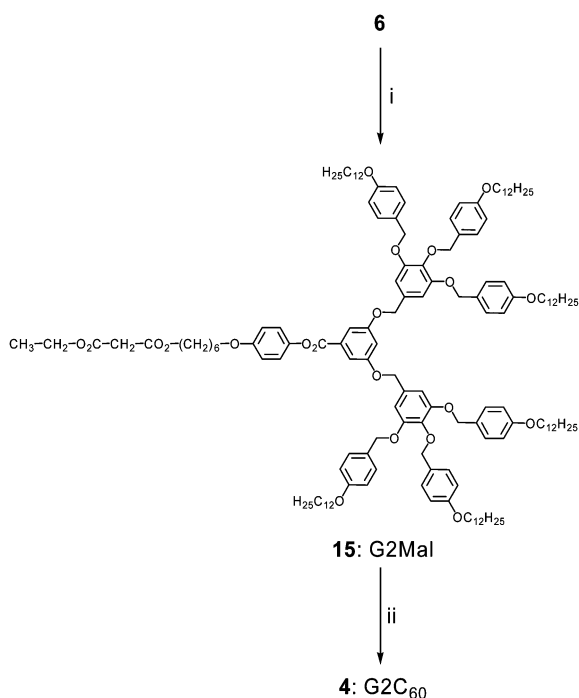

Scheme 4 (i) Ethyl malonyl chloride, Et₃N, CH₂Cl₂, r.t., overnight, 52%; (ii) C₆₀, DBU, I₂, toluene, r.t., overnight, 23%. For abbreviations, see ref. 13.

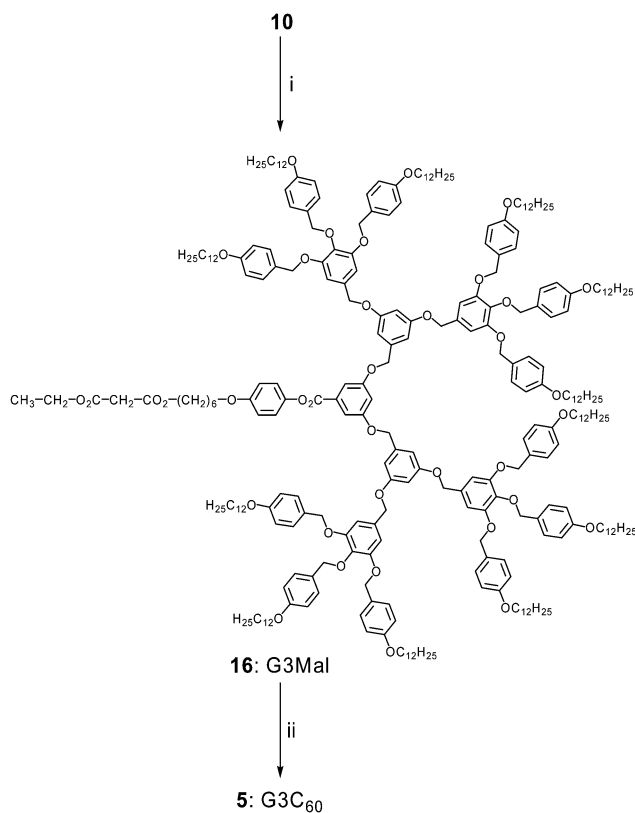

Scheme 5 (i) Ethyl malonyl chloride, Et₃N, CH₂Cl₂, r.t., overnight, 91%; (ii) C₆₀, DBU, I₂, toluene, r.t., overnight, 16%. For abbreviations, see ref. 13.

Table 1 Phase transition^a temperatures and enthalpies of dendrons **10**, **11**, and **13**, malonates **7**, **12**, and **14–16**, and methanofullerenes **1–5**

Compound	T_g /°C	Transition	Temperature/°C	ΔH /kJ mol ⁻¹
10	63	Col → I	115	11.3
11	65	Col → I	112	11.6
13		Cr → I	72 ^b	1.9
(G2) ₂ Mal (7)		Cr → Col _h - <i>p6mm</i>	73	7.8
		Col _h - <i>p6mm</i> → I	88 ^c	—
(G2) ₂ C ₆₀ (1)		Cr → I	52 ^b	18.8
(G3) ₂ Mal (12) ^d		Col _h - <i>p6mm</i> → I	109	20.7
(G3) ₂ C ₆₀ (2)	44	Col _h - <i>p6mm</i> → I	93	15.8
G2G3Mal (14)	45	Col _h - <i>p6mm</i> → I	105	18.2
G2G3C ₆₀ (3)	64	Col _h - <i>p6mm</i> → I	74	10.9
G2Mal (15)	40	Cr → Col _h - <i>p6mm</i>	56	5.1
		Col _h - <i>p6mm</i> → I	86	8.1
G2C ₆₀ (4)	36	Col _h - <i>c2mm</i> → I	68	6.8
G3Mal (16)	51	Col _h - <i>p6mm</i> → I	114	11.1
G3C ₆₀ (5)	35	Col _h - <i>p6mm</i> → I	85	7.9

^a Cr = crystalline or semicrystalline solid, T_g = glass transition temperature determined during the first cooling run, Col = columnar phase, Col_h-*p6mm* = hexagonal columnar phase of *p6mm* symmetry, Col_h-*c2mm* = rectangular columnar phase of *c2mm* symmetry, I = isotropic liquid. Temperatures are given as the onset values taken from the second heating run. ^b Temperature determined during the first heating run. ^c Determined by POM and XRD. ^d Not detected.

1 molecule of (G3)₂Mal (**12**) [equivalent to two (N_D) dendritic parts as in G3Mal (**16**), $\alpha = 180^\circ$ for each dendron] and 1 molecule of G2G3Mal (**14**) [as for (G3)₂Mal (**12**), $N_D = 2$] fitting the volume of the elemental stratum with a thickness h'' of 8.0, 8.3, and 8.3 Å, respectively. Again, a good agreement is found between h' and h'' , and this periodicity is assigned to the mean stacking distance between discs. Similarly to the hemidendrimers, the column formation results from the stacking of the supramolecular discs, the hard part of the column is filled with the poly(benzyl ether) dendron, and the inner part accommodates the malonate moiety; the columns are surrounded by the molten aliphatic chains. Note that in the supramolecular organization of (G2)₂Mal (**7**), one of the dimer shares its dendritic branches with two consecutive slices (discs) of the columns, which is permitted due to the great flexibility of the malonate spacer.

Liquid-crystalline fullerodendrimers. The non-mesomorphic character of (G2)₂C₆₀ (**1**) confirms that mesophase induction in such bulky materials requires the connection of strong liquid-crystalline promoters.¹ As for fullerodendrimers (G3)₂C₆₀ (**2**) and G2G3C₆₀ (**3**), derived from malonates (G3)₂Mal (**12**) and G2G3Mal (**14**), respectively, they both exhibit a hexagonal columnar phase. The dimensions of the hexagonal lattices were not greatly modified upon addition of C₆₀, indicating a similar paving of the two-dimensional network of these species [(G3)₂C₆₀ (**2**), G2G3C₆₀ (**3**), (G3)₂Mal (**12**), and G2G3Mal (**14**)]. The same retrostructural analysis can thus be applied here for the paving of the hexagonal lattices. However, to accommodate the bulky C₆₀ unit, the thickness of an elementary stratum of the column needs to increase to a minimum of 10 Å, *i.e.* the diameter of C₆₀. For (G3)₂C₆₀ (**2**), the planar angle of the dendritic branches is *ca.* 180°, which suggests one molecule ($Z = 1$, $N_D = 2$) to cover the hexagonal lattice and forming one

Table 2 X-Ray characterization of the mesophases

Compound	$d_{\text{exp}}/\text{\AA}^a$	$[hk]^b$	I^c	$d_{\text{theo}}/\text{\AA}^{ad}$	Parameters ^d	N_D^e
(G2) ₂ Mal (7)	35.6	10	VS (sh)	35.6	$T = 80\text{ }^\circ\text{C}$ $a = 41.1\text{ \AA}$ $S = 1460\text{ \AA}^2$ $V_{\text{mol}} = 7960\text{ \AA}^3$ $h'' \sim 8.0\text{ \AA}$, $Z = 1.5$	3
	4.6	h_{ch}	VS (br)			
(G3) ₂ Mal (12)	40.3	10	VS (sh)	40.3	$T = 90\text{ }^\circ\text{C}$ $a = 46.5\text{ \AA}$ $S = 1875\text{ \AA}^2$ $V_{\text{mol}} = 15570\text{ \AA}^3$ $h'' \sim 8.3\text{ \AA}$, $Z = 1$	2
	23.25	11	M (sh)	23.27		
	20.15	20	M (sh)	20.15		
	8.5	h'	VW (br)			
(G3) ₂ C ₆₀ (2)	4.5	h_{ch}	VS (br)		$T = 80\text{ }^\circ\text{C}$ $a = 47.05\text{ \AA}$ $S = 1920\text{ \AA}^2$ $V_{\text{mol}} = 16160\text{ \AA}^3$ $h'' \sim 16.8\text{ \AA}$, $Z = 2$	4
	40.75	10	VS (sh)	40.75		
	23.55	11	M (sh)	23.52		
	20.35	20	M (sh)	20.37		
G2G3Mal (14)	8.5	h'	VW (br)		$T = 60\text{ }^\circ\text{C}$ $a = 45.95\text{ \AA}$ $S = 1830\text{ \AA}^2$ $V_{\text{mol}} = 11540\text{ \AA}^3$ $h'' \sim 8.3\text{ \AA}$, $Z = 1$	2
	4.6	h_{ch}	VS (br)			
	39.75	10	VS (sh)	39.8		
	22.95	11	M (sh)	22.97		
G2G3C ₆₀ (3)	19.9	20	M (sh)	19.9	$T = 80\text{ }^\circ\text{C}$ $a = 46.65\text{ \AA}$ $S = 1885\text{ \AA}^2$ $V_{\text{mol}} = 12410\text{ \AA}^3$ $h'' \sim 13.2\text{ \AA}$, $Z = 2$	4
	8.0	h'	VW (br)			
	4.6	h_{ch}	VS (br)			
	40.45	10	VS (sh)	40.4		
G2Mal (15)	23.3	11	M (sh)	23.3	$T = 80\text{ }^\circ\text{C}$ $a = 46.65\text{ \AA}$ $S = 1885\text{ \AA}^2$ $V_{\text{mol}} = 12410\text{ \AA}^3$ $h'' \sim 13.2\text{ \AA}$, $Z = 2$	3
	17.5	20	M (sh)	17.6		
	8.0	h'	VW (br)			
	4.5	h_{ch}	VS (br)			
G2C ₆₀ (4)	75.15	11	VS (sh)	75.15	$T = 60\text{ }^\circ\text{C}$ $a = 133.7\text{ \AA}$ $b = 91.2\text{ \AA}$ $S = 6100\text{ \AA}^2$ $V_{\text{mol}} = 4760\text{ \AA}^3$ $h'' \sim 9.4\text{ \AA}$, $Z = 12$	12
	66.85	20	VS (sh)	66.85		
	45.5	02	S (sh)	45.6		
	39.9	31	VW (sh)	40.0		
	37.5	22	S (sh)	37.7		
	33.35	40	M (sh)	33.4		
	29.6	13	M (sh)	29.65		
	25.1	33	M (sh)	25.1		
	22.3	60	W (sh)	22.3		
	8.8	h'	W (br)			
	4.5	h_{ch}	VS (br)			
	G3Mal (16)	41.3	10	VS (sh)		
23.9		11	S (sh)	23.85		
20.6		20	S (sh)	20.65		
8.0		h'	VW (br)			
G3C ₆₀ (5)	4.6	h_{ch}	VS (br)		$T = 80\text{ }^\circ\text{C}$ $a = 45.8\text{ \AA}$ $S = 1820\text{ \AA}^2$ $V_{\text{mol}} = 8570\text{ \AA}^3$ $h'' \sim 9.4\text{ \AA}$, $Z = 2$	2
	39.8	10	VS (sh)	39.65		
	22.8	11	S (sh)	22.9		
	8.5	h'	VW (br)			
	4.6	h_{ch}	VS (br)			

^a d_{exp} and d_{theo} are the experimental and theoretical diffraction spacings, respectively. ^b $[hk]$ are the indexation of the reflections; h' and h_{ch} are short range order periodicities determined by XRD corresponding to some weak liquid-like correlations (accuracy: *ca.* $\pm 1\text{ \AA}$) and to the liquid-like order of the molten chains, respectively. ^c Intensity of the reflections: VS: very strong, S: strong, M: medium, W: weak, VW: very weak; br: broad, sh: sharp. ^d d_{theo} is deduced from the lattice parameters a (Col_h) or a and b (Col_r) from the following mathematical expressions: i) for Col_h, $a = 2 \times [\sum_{hk} d_{hk} \cdot (h^2 + k^2 + hk)^{3/2}] / \sqrt{3N_{hk}}$ where N_{hk} is the number of hk reflections. S is the lattice area: $S = a^2\sqrt{3}/2$; ii) for Col_r, $S = a \times b/2$ and $\langle d_{hk} \rangle = 1/[(h^2/a^2 + k^2/b^2)^{1/2}]$. Z is the aggregation number or the number of molecular equivalents per stratum of column. V_{mol} is the molecular volume: $V_{\text{mol}} = V_{\text{C60}} + V_{\text{malonate}}$, where $V_{\text{C60}} = 700\text{ \AA}^3$, $V_{\text{malonate}} = (\text{MW}/0.6022) \times (V_{\text{CH}_2}(T)/V_{\text{CH}_2}(T_0))$, MW the molecular weight of the malonate and $V_{\text{CH}_2} = 26.5616 + 0.02023T$. h'' is the theoretical intracolumnar repeating distance, deduced from the measured molecular volume and the columnar cross-section, $h'' = Z \times V_{\text{mol}}/S$. ^e N_D : number of dendritic branches per stratum.

stratum ($h'' = 8.4\text{ \AA}$) as in (G3)₂Mal (12). However, such a height of column is not compatible with the molecular thickness imposed by C₆₀. Consequently, two molecules of (G3)₂C₆₀ (2) were considered to define one slice of column ($h'' = 2 \times h'$), with h' corresponding to the average distance between two consecutive discs (*i.e.* the thickness of the dendritic branches). Similarly, for the

mixed fullerodendrimer G2G3C₆₀ (3), one molecule was first considered, by analogy to its malonate precursor, leading to a columnar slice thickness of *ca.* 6.6 \AA , incompatible with the size of C₆₀. As above, two molecules were thus considered to match the structural requirements. Note that for fullerodendrimers bearing two dendritic branches, non-integer Z values are unlikely

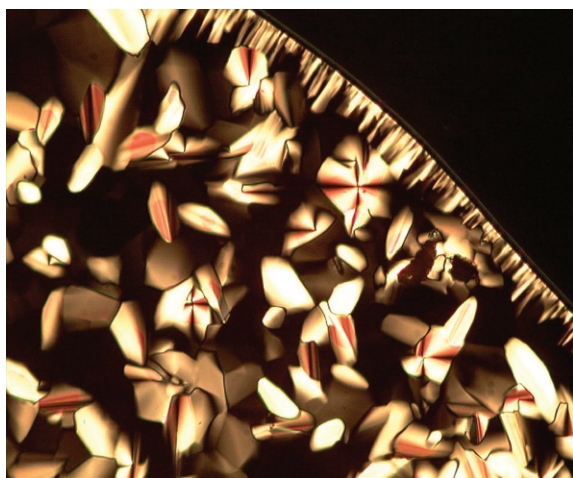


Fig. 1 Thermal polarized optical micrograph of the texture displayed by G3C₆₀ (**5**) in the hexagonal columnar phase at 84 °C.

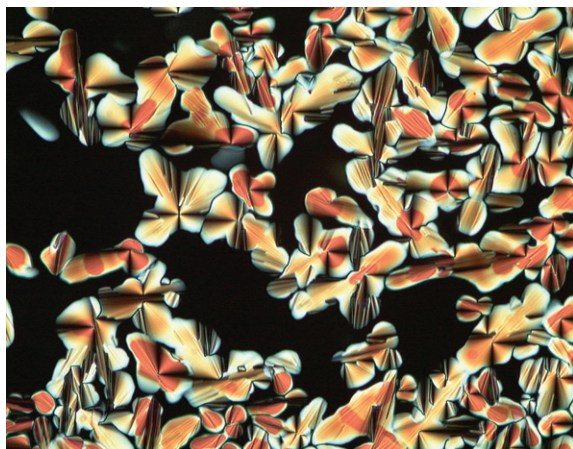


Fig. 2 Thermal polarized optical micrograph of the texture displayed by G2Mal (**15**) in the hexagonal columnar phase at 85 °C.


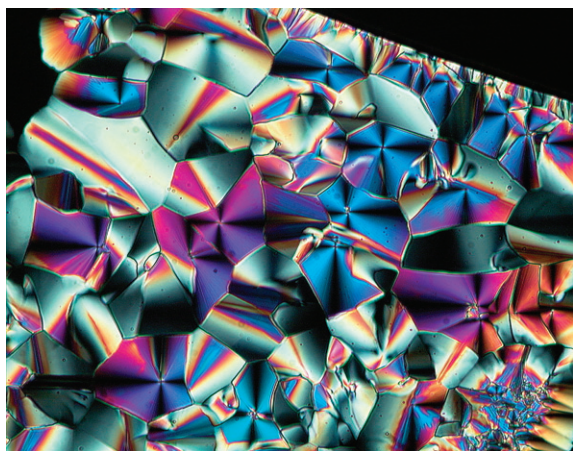


Fig. 3 Thermal polarized optical micrograph of the texture displayed by (G2)₂Mal (**7**) in the hexagonal columnar phase at 79 °C.

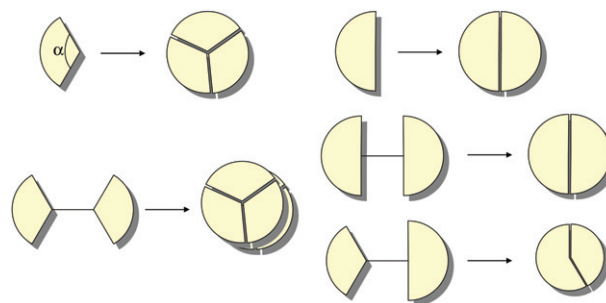

Scheme 6 Schematic representation of the formation of supramolecular discs with hemidendritic and dendritic systems. The supramolecular organization of the fullerodendrimers is derived from that of the malonate precursors. For details, see Table 2 and main text.

(the molecules are no longer dimers, C₆₀ is indeed indivisible). For this compound, the discrepancy between the two periodicities is likely due to a deficit of dendritic branches, not large enough to fully embed C₆₀, with h' representing the interdisc distance over a short range correlation length. Thus, the larger hexagonal cells with a thickness h'' of 16.8 and 13.2 Å, respectively, incorporate 2 molecular equivalents of (G3)₂C₆₀ (**2**) and G2G3C₆₀ (**3**). In both arrangements, the C₆₀ units are located towards the interior of the column, and loosely stacked along the columnar axis, surrounded by the dendritic part.

Rectangular and hexagonal columnar phases are obtained for hemidendrimers G2C₆₀ (**4**) and G3C₆₀ (**5**), respectively. The lattice parameter of the hexagonal columnar phase on going from G3Mal (**16**) to G3C₆₀ (**5**) remains almost constant, so that the same packing mode is likely reproduced, and for an equivalent surface to pave, two molecules per lattice were considered leading to a cell thickness h'' of 9.4 Å. In this case, the thickness is compatible with aggregates of C₆₀ if some kind of close compact-like (hexagonal or cubic) arrangement of C₆₀ in the centre of the column is considered ($h'' \sim \phi\sqrt{3}/2$, $\phi \sim 10$ Å = diameter of C₆₀), which is allowed since only one dendritic branch is attached to C₆₀, encouraging C₆₀-C₆₀ interactions through the “unprotected face”.^{5a} However, for G2C₆₀ (**4**), the situation is slightly more complicated since the expansion of the cell occurs in the symmetry plane as well as along the column. The section area S of the column is almost quadrupled on going from G2Mal (**15**) to G2C₆₀ (**4**). Considering that the dendritic parts adopt in both cases a flat conformation and that each tapered dendron paves a similar surface area, the number of fullerodendrimers should also be quadrupled. Thus, at least twelve molecules of G2C₆₀ (**4**) are considered in the elementary columnar slice, with a thickness h'' of 9.4 Å, which is identical to the value found for G3C₆₀ (**5**). The average stacking distance, h' , between consecutive disc-like [G3C₆₀ (**5**)] or discoid-like [G2C₆₀ (**4**)] assemblies remains the same. Such a non-circular arrangement was also found in related systems,^{5a} and the rather low thickness value was attributed to the close packing of C₆₀ into aggregates forming the centre of the column. Thus, the packing of G2C₆₀ (**4**) and G3C₆₀ (**5**) is different to that of (G3)₂C₆₀ (**2**) and G2G3C₆₀ (**3**) in the sense that for (G3)₂C₆₀ (**2**) and G2G3C₆₀ (**3**) the packing and the C₆₀ interactions are rather loose whilst for G2C₆₀ (**4**) and G3C₆₀ (**5**) the C₆₀ units self-assemble into aggregates, which grow along the columnar axis.

In order to confirm the above arrangements, molecular dynamics experiments on compound G2G3C₆₀ (**3**) were performed. Two minimized structures of G2G3C₆₀ (**3**) were placed in a hexagonal cell, where only the thickness was fixed ($h'' = 13 \text{ \AA}$), and the molecules were only allowed to expand laterally.

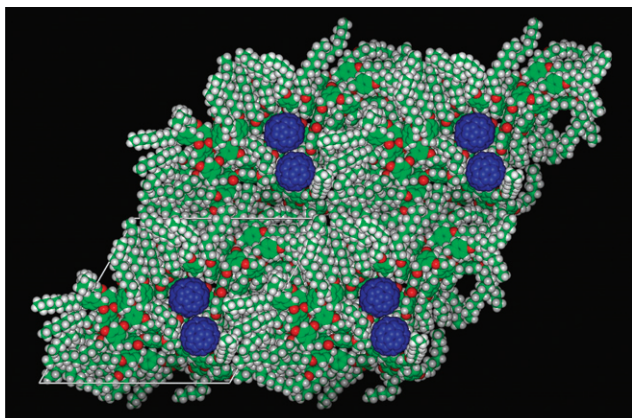


Fig. 4 Top view of the supramolecular organization of G2G3C₆₀ (**3**) within the hexagonal columnar phase of $p6mm$ symmetry.

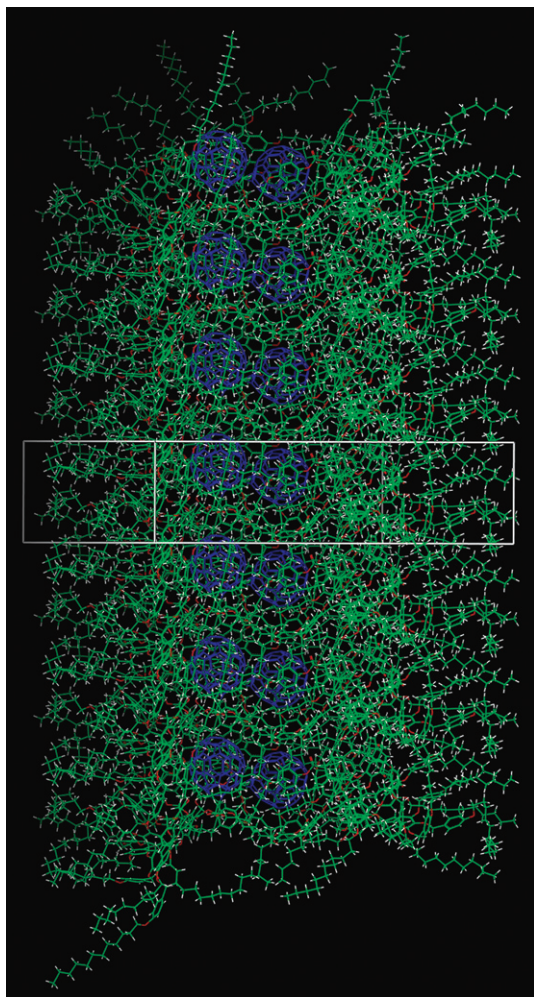


Fig. 5 Side view of the supramolecular organization of G2G3C₆₀ (**3**) within the hexagonal columnar phase of $p6mm$ symmetry.

The results of the dynamics experiments are in agreement with the experimental data: a lattice parameter comparable to that of the X-ray experiments and a density close to unity were found. Moreover, a perfect paving of the surface and a dense occupation of the available volume were confirmed (Fig. 4 and 5).

Conclusion

In order to design fullerodendrimers which display columnar mesomorphism, C₆₀ was functionalized *via* the Bingel reaction with symmetrical and non-symmetrical malonates which carry poly(benzyl ether) dendrons as liquid-crystalline promoters. The liquid-crystalline malonates were prepared by applying a modular synthetic approach. Hemidendrimers were also synthesized. All the malonate and fullerene derivatives give rise to columnar phases. The supramolecular organization of the malonate and fullerene derivatives within the columnar phases is governed by the dendrimer. Indeed, for the fullerodendrimers, C₆₀ has no (or little) influence on the structure of the mesophases providing the size of the dendritic addends is large enough, *i.e.* when two third-generation dendrons [compound (G3)₂C₆₀ (**2**)], or one third-generation and one second-generation [compound G2G3C₆₀ (**3**)] dendron are associated, or for a third-generation hemidendrimer [compound G3C₆₀ (**5**)]. If the dendron is not large enough to encapsulate C₆₀, the latter influences the organization as observed for compound G2C₆₀ (**4**) (second-generation hemidendrimer) which gives rise to a rectangular columnar phase whereas its malonate precursor shows a hexagonal columnar phase. The design of fullerene-containing liquid crystals with tailor-made properties requires that the influence of C₆₀ is drastically minimized and even suppressed. This work and former studies^{1,5b} confirm that functionalization of C₆₀ with liquid-crystalline dendrimers is an elegant strategy for the design of fullerene-containing liquid crystals for which the mesomorphism and supramolecular organization can be controlled by design.

Acknowledgements

RD thanks the Swiss National Science Foundation (Grant No. 200020-111681) for financial support. BD and DG thank Dr C. Bourgogne for modelling experiments and CNRS-Université Louis Pasteur for constant support.

References

- 1 R. Deschenaux, B. Donnio and D. Guillon, *New J. Chem.*, 2007, **31**, 1064.
- 2 (a) M. Sawamura, K. Kawai, Y. Matsuo, K. Kanie, T. Kato and E. Nakamura, *Nature*, 2002, **419**, 702; (b) Y. Matsuo, A. Muramatsu, R. Hamasaki, N. Mizoshita, T. Kato and E. Nakamura, *J. Am. Chem. Soc.*, 2004, **126**, 432; (c) Y. Matsuo, A. Muramatsu, Y. Kamikawa, T. Kato and E. Nakamura, *J. Am. Chem. Soc.*, 2006, **128**, 9586.
- 3 M. Kimura, Y. Saito, K. Ohta, K. Hanabusa, H. Shirai and N. Kobayashi, *J. Am. Chem. Soc.*, 2002, **124**, 5274.
- 4 R. J. Bushby, I. W. Hamley, Q. Liu, O. R. Lozman and J. E. Lydon, *J. Mater. Chem.*, 2005, **15**, 4429.
- 5 (a) J. Lenoble, N. Maringa, S. Campidelli, B. Donnio, D. Guillon and R. Deschenaux, *Org. Lett.*, 2006, **8**, 1851; (b) J. Lenoble, S. Campidelli, N. Maringa, B. Donnio, D. Guillon, N. Yevlampieva and R. Deschenaux, *J. Am. Chem. Soc.*, 2007, **129**, 9941.

- 6 J.-F. Nierengarten, N. Solladié and R. Deschenaux, in *Fullerenes: Principles and Applications*, ed. F. Langa and J.-F. Nierengarten, RSC Publishing, Cambridge, UK, 2007, ch. 5, pp. 127–151.
- 7 (a) I. M. Saez and J. W. Goodby, *J. Mater. Chem.*, 2005, **15**, 26; (b) B. Donnio and D. Guillon, *Adv. Polym. Sci.*, 2006, **201**, 45; (c) B. Donnio, S. Buathong, I. Bury and D. Guillon, *Chem. Soc. Rev.*, 2007, **36**, 1495.
- 8 (a) V. Percec, C.-H. Ahn, W.-D. Cho, A. M. Jamieson, J. Kim, T. Leman, M. Schmidt, M. Gerle, M. Möller, S. A. Prokhorova, S. S. Sheiko, S. Z. D. Cheng, A. Zhang, G. Ungar and D. J. P. Yearley, *J. Am. Chem. Soc.*, 1998, **120**, 8619; (b) V. Percec, W.-D. Cho, G. Ungar and D. J. P. Yearley, *J. Am. Chem. Soc.*, 2001, **123**, 1302; (c) V. Percec, M. Glodde, T. K. Bera, Y. Miura, I. Shiyanovskaya, K. D. Singer, V. S. K. Balagurusamy, P. A. Heiney, I. Schnell, A. Rapp, H.-W. Spiess, S. D. Hudson and H. Duan, *Nature*, 2002, **419**, 384; (d) G. Ungar, Y. Liu, X. Zeng, V. Percec and W.-D. Cho, *Science*, 2003, **299**, 1208; (e) V. Percec, M. R. Imam, T. K. Bera, V. S. K. Balagurusamy, M. Peterca and P. A. Heiney, *Angew. Chem., Int. Ed.*, 2005, **44**, 4739; (f) V. Percec, A. E. Dulcey, M. Peterca, M. Ilić, M. J. Sienkowska and P. A. Heiney, *J. Am. Chem. Soc.*, 2005, **127**, 17902.
- 9 D. Scanu, N. P. Yevlampieva and R. Deschenaux, *Macromolecules*, 2007, **40**, 1133.
- 10 (a) C. J. Hawker and J. M. J. Fréchet, *J. Am. Chem. Soc.*, 1990, **112**, 7638; (b) S. M. Grayson and J. M. J. Fréchet, *Chem. Rev.*, 2001, **101**, 3819; (c) J. M. J. Fréchet, *J. Polym. Sci., Part A: Polym. Chem.*, 2003, **41**, 3713.
- 11 (a) C. Bingel, *Chem. Ber.*, 1993, **126**, 1957; (b) J.-F. Nierengarten, A. Herrmann, R. R. Tykwinski, M. Rüttimann, F. Diederich, C. Boudon, J.-P. Gisselbrecht and M. Gross, *Helv. Chim. Acta*, 1997, **80**, 293; (c) X. Camps and A. Hirsch, *J. Chem. Soc., Perkin Trans. 1*, 1997, 1595.
- 12 D. Lacey, H. N. Beattie, G. R. Mitchell and J. A. Pople, *J. Mater. Chem.*, 1998, **8**, 53.
- 13 Abbreviations: r.t., room temperature; DBU, 1,8-diazabicyclo [5.4.0]undec-7-ene; DCC, *N,N'*-dicyclohexylcarbodiimide; DPTS, 4-(dimethylamino)pyridinium toluene-*p*-sulfonate; 4-Ppy, 4-pyrrolidinopyridine.
- 14 (a) B. Dardel, D. Guillon, B. Heinrich and R. Deschenaux, *J. Mater. Chem.*, 2001, **11**, 2814; (b) S. Campidelli, J. Lenoble, J. Barberá, F. Paolucci, M. Marcaccio, D. Paolucci and R. Deschenaux, *Macromolecules*, 2005, **38**, 7915.